


ACR-A(E)-1-3

This document is intended to be used in conjunction with SMARTCOAT™ 3-part specifications for comprehensive project and application instructions.

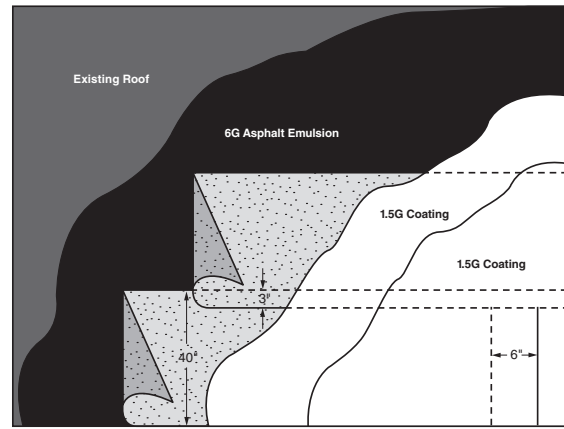

SUBSTRATE:

Existing roof: Modified bitumen (APP or SBS), smooth or granule surface, built-up-roof (BUR)

LIMITED WARRANTY DURATION

10 years. See SMARTCOAT Warranty Overview for warranty protocol and guidelines.

SUMMARY OF MEMBRANE MATERIALS

Component	Gallons/100 sq. ft. or Ply	Dry Mils
100 Roof Wash	Roof condition dependent	100 Roof Wash must be completely rinsed and roof surface dry
220 Asphalt Emulsion	6	37
501 Reinforcement	1	6
400/401 Acrylic Coating	1.5	12
400/401 Acrylic Coating	1.5	12

Total System Wet/Dry Mils and Weight per 100 Square Feet (Approximate)

Wet Mils	Dry Mils (400/401)	Weight (lbs.)
144	67/69	48

SUMMARY OF FLASHING MATERIALS:

Components may include:

- 400/401 Acrylic Coating
 - 300/301 Acrylic Non-Fibered/Fibered Mastic
 - 370 UltraSeal
 - SMARTFAB 500 Polyester Reinforcement
- See *SMARTCOAT Construction Details* or *SMARTCOAT Applicator's Guide* for detail-specific instruction.

SUMMARY OF APPLICATION:

1. Clean roof surface thoroughly, including APP-modified membranes utilized for large repair areas. Use SMARTCOAT Roof Wash as needed to ensure roof surface is clean and dry;
2. Seal all deficiencies in the existing roof with appropriate flashing materials (see Summary of Flashing Materials);
3. Apply SMARTCOAT 220 Asphalt Emulsion at a rate of 6 gallons per 100 sq. ft (96 wet mils); immediately embed SMARTFAB 501 Polyester Reinforcement - do not submerge reinforcement in emulsion or walk-in while

wet; allow to cure for a minimum of 2 days, environmental conditions may lengthen cure period; when cured, 220 is black and will not distort or show signs of an impression when a thumb is pressed onto the surface and rotated ninety degrees;

4. Once cured, power wash emulsion to remove any oils or surfactants;
5. Once dry, apply base coat of SMARTCOAT 400 ACRYLIC COATING at the rate of 1.5 gallons per 100 sq. ft. (24 wet mils);
6. Once dry, apply top coat of SMARTCOAT 400 ACRYLIC COATING at the rate of 1.5 gallons per 100 sq. ft. (24 wet mils).

NOTE: On roofs with greater than 3:12 slope or on vertical surfaces, it is not recommended to apply more than 1G per 100 sq. ft. in a single coat to avoid material sagging.